

EuCo₂P₂: A Model Molecular-Field Helical Heisenberg Antiferromagnet

N. S. Sangeetha, Abhishek Pandey,* and D. C. Johnston†

Ames Laboratory and Department of Physics and Astronomy, Iowa State University, Ames, Iowa 50011, USA

(Dated: December 10, 2015)

The Eu spins-7/2 in EuCo₂P₂ with the tetragonal ThCr₂Si₂-type structure have the prototypical noncollinear helical antiferromagnetic structure below the Néel temperature $T_N = 66.5$ K as previously determined from single-crystal neutron diffraction measurements. The helix axis is along the c axis with the ordered moments aligned within the ab plane. Our recent formulation of molecular field theory (MFT) is found to quantitatively fit the anisotropic magnetic susceptibility of single-crystal EuCo₂P₂ at $T \leq T_N$ with a helix turn angle comparable to the neutron diffraction value. The experimental and MFT magnetic heat capacities at $T \leq T_N$ are also in good agreement. Values of the Heisenberg exchange interactions between the Eu spins-7/2 within the J_0 - J_{z1} - J_{z2} MFT model are derived. The results demonstrate the robust applicability of the MFT to model the thermodynamic properties of noncollinear Heisenberg antiferromagnets.

We recently presented a general formulation of the Weiss molecular field theory (MFT) of local-moment Heisenberg antiferromagnets (AFMs) containing identical crystallographically-equivalent spins [1–3]. In this formulation the paradigm of magnetic sublattices previously required to calculate the magnetic and thermal properties below the AFM ordering (Néel) temperature T_N was abandoned and thermodynamic predictions for various systems were obtained from consideration of only the exchange interactions between a central moment and its neighbors. This formulation allows the anisotropic temperature T -dependent magnetic susceptibility χ and the magnetic heat capacity $C_{\text{mag}}(T)$ of collinear and planar noncollinear AFMs at $T \leq T_N$ to be calculated on the same footing. Furthermore, the theoretical predictions are cast in terms of measurable properties. For collinear AFMs these are the spin S , T_N , $\chi(T_N)$ and the Weiss temperature θ_p in the Curie-Weiss law for χ in the paramagnetic state. For planar noncollinear AFMs an additional parameter is required. In the J_0 - J_{z1} - J_{z2} MFT model for a helical AFM structure [1, 2], the additional parameter is the turn angle kd between ordered moments in adjacent magnetic moment layers along the helix axis. Several applications of this MFT to fit experimental $\chi(T \leq T_N)$ data for single crystals and polycrystals of collinear and planar noncollinear AFM systems have been presented [1, 3–10].

However, the MFT predictions have not yet been compared with single-crystal $C_{\text{mag}}(T)$ and $\chi(T)$ data for any system with a (coplanar) helix AFM structure, which is the prototype for a noncollinear AFM structure. The reason is that no such data were available for a helical structure in which the assumptions of the MFT are fulfilled, namely high spin (small quantum fluctuations), dominant Heisenberg spin interactions, and no ferromagnetic (FM) component or magnetic and/or spin reorientation transitions occurring below the initial T_N . Furthermore, for a definitive test of the applicability of the MFT predictions for a helix, one also requires input about the AFM structure from neutron diffraction measurements.

Single-crystal neutron diffraction measurements [11] have shown that EuCo₂P₂ has the required helical AFM structure below $T_N = 66.5$ K. A generic picture of such a helix is shown in Fig. 1 of [1]. EuCo₂P₂ has the body-centered tetragonal (bct) ThCr₂Si₂-type crystal structure (space group $I4/mmm$) [12]. The lattice parameters of EuCo₂P₂ at room temperature are $a = 3.7649(5)$ Å and $c = 11.348(2)$ Å with $c/a = 3.014(1)$ [12]. The ordered moment at 15 K is $\langle \mu \rangle = 6.9(1)$ μ_B/Eu , which agrees with the saturation moment $\mu_{\text{sat}} = gS\mu_B/\text{Eu} = 7\mu_B/\text{Eu}$ expected for Eu⁺² spin $S = 7/2$ and spectroscopic splitting factor $g = 2$ [11]. The authors of [11] reported that the AFM structure below T_N is a helix with the Eu ordered moments aligned in the ab plane of the tetragonal structure, with the helix axis along the perpendicular c axis. The ab -plane alignment of the ordered moments is consistent with the prediction of magnetic dipole interactions between the Eu spins for the above c/a ratio [13]. The incommensurate AFM propagation vector for the helix changed by only 2% from $\mathbf{k} = [0, 0, 0.834(4)]2\pi/c$ at $T = 64$ K to $[0, 0, 0.852(4)]2\pi/c$ at $T = 15$ K [11]. Since $d = c/2$ is the distance along the c axis between adjacent layers of FM-aligned moments in the bct Eu sublattice, the turn angle kd between the ordered moments in adjacent layers perpendicular to the helix axis is

$$kd(64 \text{ K}) = 0.834(4)\pi \text{ rad}, \quad kd(15 \text{ K}) = 0.852(4)\pi \text{ rad}. \quad (1)$$

Polycrystalline samples of EuCo₂P₂ exhibit AFM ordering of the Eu⁺² spins at $T_N = 66.5(5)$ K as deduced from powder $\chi(T)$ data [14]. The data in the paramagnetic state at $T > T_N$ follow the Curie-Weiss law $\chi = \frac{C}{T - \theta_p}$ where the positive $\theta_p = 20(2)$ K [14] indicates dominant FM interactions [1, 2]. The effective moment obtained from the observed Curie constant is $\mu_{\text{eff}} = 8.10(8)$ $\mu_B/\text{f.u.}$, where f.u. means formula unit. This value is close to the value $\mu_{\text{eff}}^{\text{calc}} = g\sqrt{S(S+1)}\mu_B = 7.94 \mu_B$ calculated from Eu⁺² spin $S = 7/2$ with $g = 2$. The authors' ¹⁵¹Eu Mössbauer data are also consistent

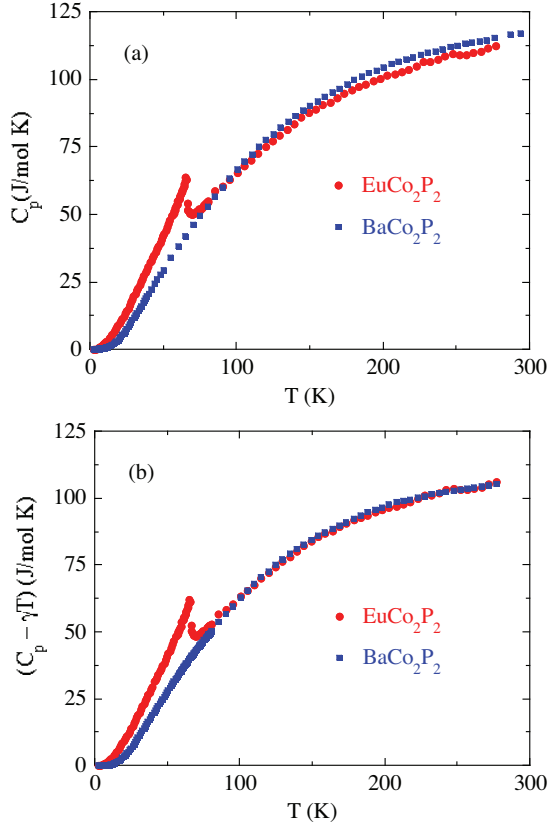


FIG. 1: (Color online) (a) C_p versus T for EuCo_2P_2 and BaCo_2P_2 . (b) The difference $C_p - \gamma T$ versus T for EuCo_2P_2 and BaCo_2P_2 , where γ is the Sommerfeld electronic heat capacity coefficient for the respective compound.

with the oxidation state Eu^{+2} , and they inferred that Co does not contribute to the AFM ordering in EuCo_2P_2 [14]. The values of kd with $\pi/2 < kd < \pi$ in Eq. (1) indicate that the dominant *interlayer* interactions are AFM [see Eq. (3a) below], and the above θ_p value therefore indicates that the dominant *intralayer* interactions must be FM [see Eq. (3c) below]. Electrical resistivity $\rho(T)$ measurements on single crystals indicate metallic character with a sharp break in slope at T_N [15].

In order to test the applicability of our formulation of MFT to the noncollinear AFM state of EuCo_2P_2 we grew crystals of EuCo_2P_2 and measured their properties. We find that this compound is a model system exhibiting an anisotropic $\chi(T)$ at $T \leq T_N$ that is well described by the MFT for a helical AFM structure with turn angles comparable to the neutron diffraction results in Eq. (1). We also present $C_{\text{mag}}(T)$ data and show that the MFT prediction is in good agreement with these data for $T \leq T_N$. An independent measurement of T_N was obtained from in-plane $\rho(T)$ measurements. Finally, the Heisenberg exchange interactions between the Eu spins are estimated within a minimal J_0 - J_{z1} - J_{z2} MFT model.

Our crystals of EuCo_2P_2 were grown in Sn flux as de-

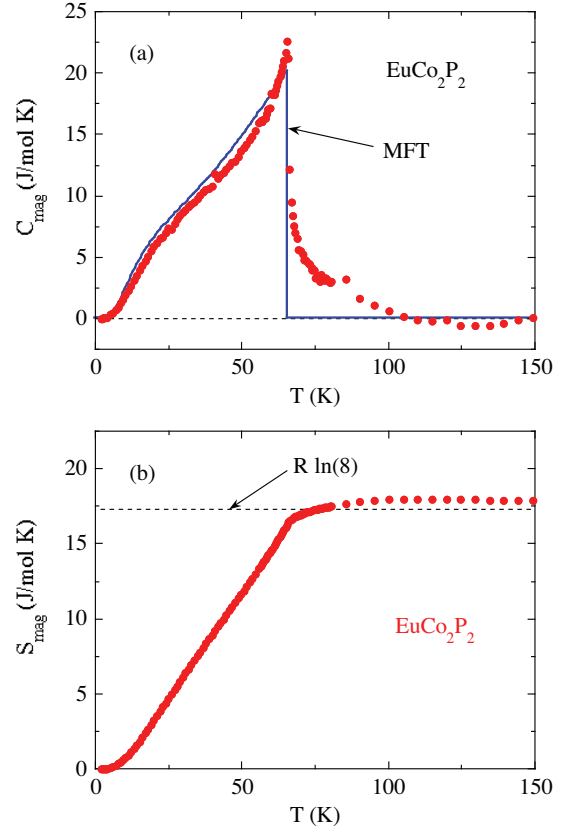


FIG. 2: (Color online) (a) C_{mag} versus T for EuCo_2P_2 (open circles). The solid curve is the prediction of MFT. (b) S_{mag} versus T for EuCo_2P_2 . The horizontal dashed line is the theoretical high- T limit $S_{\text{mag}} = R \ln(2S + 1)$ for $S = 7/2$.

scribed previously [11], whereas a polycrystalline sample of BaCo_2P_2 was prepared by solid-state reaction. Magnetization M data were obtained using the SQUID magnetometer in a Quantum Design, Inc., MPMS system for applied magnetic fields $H \leq 5.5$ T and using a vibrating sample magnetometer in a PPMS system for high-field $M(H)$ isotherm measurements up to 14 T. $C_p(T)$ and $\rho(T)$ data were also obtained using the PPMS system.

C_p data for EuCo_2P_2 and BaCo_2P_2 are plotted versus T in Fig. 1(a). The data for BaCo_2P_2 are used to correct for C_p contributions in EuCo_2P_2 from other than the Eu magnetism. A pronounced peak is seen for EuCo_2P_2 at $T_N = 65.7(1)$ K that is comparable with the previously-reported T_N values [11, 14, 15]. At low T the data for EuCo_2P_2 and BaCo_2P_2 follow $C_p = \gamma T + \beta T^3$, where $\gamma(\text{EuCo}_2\text{P}_2) = 23.7(5)$ and $\gamma(\text{BaCo}_2\text{P}_2) = 37.3(3)$ mJ/(mol K²) (not shown). The nonzero values of the Sommerfeld coefficients γ indicate metallic character for both compounds. Shown in Fig. 1(b) are the C_p data corrected for the respective electronic γT terms. One sees that the $C_p - \gamma T$ data for the two compounds are now nearly identical above ≈ 100 K. To eliminate the residual average deviation of the data

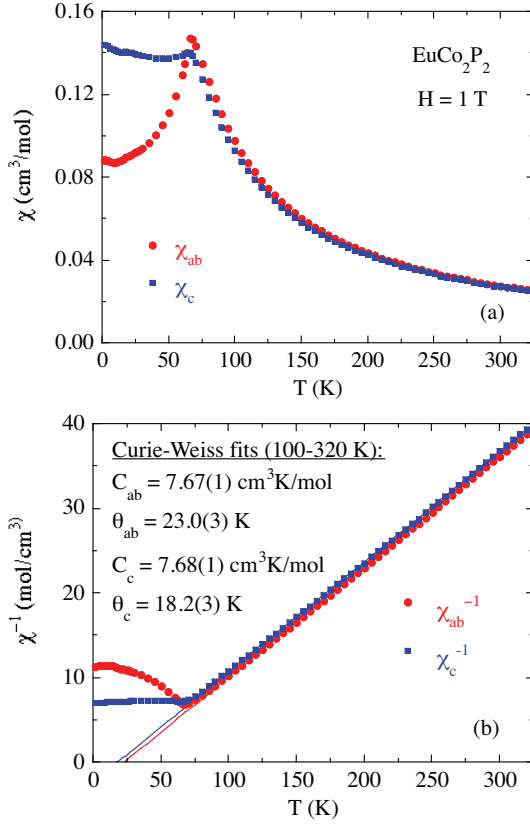


FIG. 3: (Color online) (a) $\chi \equiv M/H$ versus T for single-crystal EuCo_2P_2 for $H \parallel c$ axis and $H \parallel ab$ plane with $H = 1$ T. (b) χ^{-1} versus T for both $H \parallel c$ and $H \parallel ab$. The data above 100 K are fitted by the Curie-Weiss law (straight lines) with the fit parameters listed.

between the two compounds in the 100–300 K temperature range we multiplied the $C_p - \gamma T$ data for EuCo_2P_2 by 1.0046. Then taking the difference between the resulting data for EuCo_2P_2 and the $C_p - \gamma T$ data for BaCo_2P_2 yields the magnetic heat capacity $C_{\text{mag}}(T)$ for EuCo_2P_2 in Fig. 2(a). The nonzero C_{mag} for $T_N < T \lesssim 100$ K is due to weak dynamic short-range magnetic ordering of the Eu spins above T_N . The MFT prediction [2] for $C_{\text{mag}}(T)$ for $S = 7/2$ and $T_N = 65.7$ K is shown as the solid blue curve in Fig. 2(a). The agreement is quite good, apart from the 30 K region above T_N where the short-range magnetic ordering there is not included in the MFT prediction.

The magnetic entropy $S_{\text{mag}}(T)$ is calculated using $S_{\text{mag}}(T) = \int_0^T [C_{\text{mag}}(T)/T] dT$ and the result is shown in Fig. 2(b). The high- T limit for a mole of spins $S = 7/2$ is $R \ln(2S+1)$, where R is the molar gas constant, as shown by the horizontal dashed line in Fig. 2(b). One sees that the high- T $S_{\text{mag}}(T)$ data for EuCo_2P_2 closely approach this value. The small residual deviation is likely due to a small inaccuracy in the background C_p subtraction. The short-range magnetic ordering seen in C_{mag} at $T > T_N$

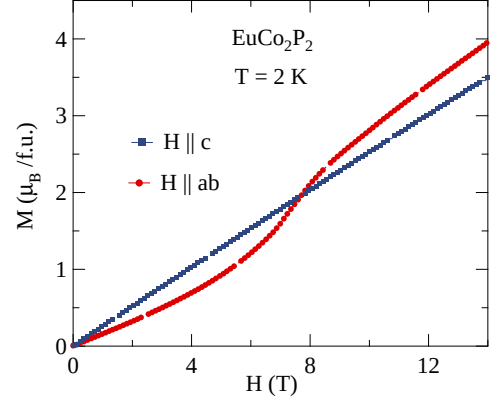


FIG. 4: (Color online) M versus H at $T = 2$ K up to high fields for $H \parallel c$ and $H \parallel ab$.

in Fig. 2(a) represents only a small fraction of the total entropy of the disordered spin system, since the change in S_{mag} from T_N to 100 K is found from Fig. 2(b) to be only about 7% of the disordered entropy $R \ln(8)$.

We also carried out in-plane $\rho(T)$ measurements on a EuCo_2P_2 crystal and the results (not shown) are similar to those in [15]. In particular, on cooling we find that the $\rho(T)$ shows a sharp increase in slope at $T_N = 66(1)$ K, consistent with our C_{mag} measurement of T_N above.

The $\chi \equiv M/H$ data are presented versus T for $H = 1$ T in Fig. 3(a) for both $H \parallel c$ axis and $H \parallel ab$ plane. The discontinuities in the slope versus T occur at $T_N \approx 66.5$ K, in agreement with the previous reports [11, 14, 15]. The $\chi(T)$ data for $H \parallel c$ become nearly independent of T below T_N , consistent with the MFT prediction [2] for the perpendicular susceptibility of the helical AFM structure of EuCo_2P_2 in which the ordered moments are oriented within the ab plane [11]. The data for $H \parallel ab$ have a nonzero limit at $T \rightarrow 0$, again consistent with the planar noncollinear AFM structure [1, 2, 9].

The inverse susceptibility χ^{-1} versus T is shown in Fig. 3(b). The data from 100 K to 320 K were fitted by the Curie-Weiss law, yielding the Curie constants and Weiss temperatures listed in the figure. Since the Curie constants are the same for the two field directions, the effective moments derived from them are also the same, $\mu_{\text{eff}} = 7.84 \mu_B/\text{f.u.}$, which agrees within about 1% with the value $7.94 \mu_B/\text{f.u.}$ expected for Eu^{+2} with $S = 7/2$ and $g = 2$. The difference $\theta_{ab} - \theta_c$ arises mainly from magnetic dipole interactions between the Eu spins [13]. The spherical average of the fitted Weiss temperatures is $\theta_{\text{p,ave}} = 21.4(3)$ K, in agreement with the previous result $\theta_p = 22(2)$ K [14] for a polycrystalline sample.

High-field $M(H)$ isotherm data at $T = 2$ K for $H \parallel c$ axis and $H \parallel ab$ plane are shown in Fig. 4. The data for $H \parallel c$ are nearly linear in field, in agreement with the high-field behavior expected within MFT for a field per-

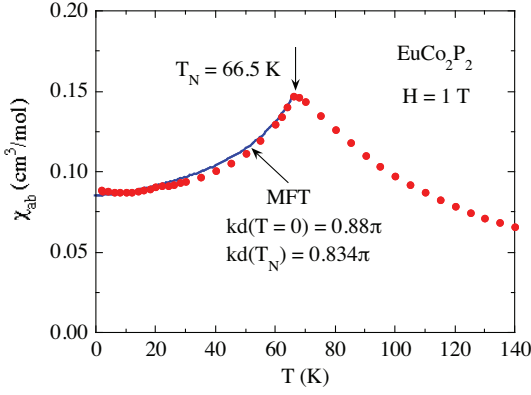


FIG. 5: (Color online) $\chi_{ab}(T)$ versus T for $H \parallel ab$ plane in $H = 1$ T. The fit by MFT for $\chi_{ab}(T)$ of a helix in Eqs. (2) for $T \leq T_N$ is shown as the solid blue curve.

pendicular to the ordering plane of a noncollinear AFM [2]. Extrapolating the $M_c(H)$ data in Fig. 4 to the saturation moment $\mu_{\text{sat}} = gS\mu_B = 7 \mu_B/\text{Eu}$ gives the critical field $H_c(T \rightarrow 0) \sim 28$ T at which a second-order transition to the paramagnetic state occurs with increasing H [2]. For the in-plane $H \parallel ab$, the $M_{ab}(H)$ data in Fig. 4 show a metamagnetic transition at ≈ 8 T. The significant width of this transition is consistent with a noncollinear AFM structure in $H = 0$ with the ordered moments aligned in the ab plane. The $M_{ab}(H)$ behavior at high H has not yet been worked out in detail for a helical AFM.

An expanded plot of $\chi_{ab}(T)$ for EuCo_2P_2 from Fig. 3(a) is shown in Fig. 5. The normalized in-plane susceptibility $\chi_{ab}(T \leq T_N)/\chi(T_N)$ for a planar noncollinear helical AFM system is given within our formulation of MFT by [1, 2]

$$\frac{\chi_{ab}(T \leq T_N)}{\chi(T_N)} = \frac{(1 + \tau^* + 2f + 4B^*)(1 - f)/2}{(\tau^* + B^*)(1 + B^*) - (f + B^*)^2}, \quad (2a)$$

where

$$B^* = 2(1 - f) \cos(kd) [1 + \cos(kd)] - f, \quad (2b)$$

$$t = \frac{T}{T_N}, \quad f = \frac{\theta_p}{T_N}, \quad \tau^*(t) = \frac{(S+1)t}{3B'_S(y_0)}, \quad y_0 = \frac{3\bar{\mu}_0}{(S+1)t}, \quad (2c)$$

the ordered moment versus T in $H = 0$ is denoted by μ_0 , the reduced ordered moment $\bar{\mu}_0 = \mu_0/\mu_{\text{sat}}$ is determined by solving $\bar{\mu}_0 = B_S(y_0)$, $B'_S(y_0) = [dB_S(y)/dy]|_{y=y_0}$ and our unconventional definition of the Brillouin function $B_S(y)$ is given in [1, 2].

We fitted the data in Fig. 5 for $T \leq T_N$ by Eqs. (2) using $S = 7/2$, $T_N = 66.5$ K, $\chi(T_N) = 0.147 \text{ cm}^3/\text{mol}$ and $f = \theta_{ab}/T_N = 0.346$ where $\theta_{ab} = 23.0$ K. For $kd(T)$ we used the value $kd(T = 64 \text{ K}) = 0.834\pi$ rad from Eq. (1) [11]. In order to fit the lowest- T data in Fig. 5, we used

$kd(T = 0) = 0.88\pi$ rad, which is comparable to the value at 15 K in Eq. (1) [11]. For intermediate temperatures kd was linearly interpolated between these two values. The $\chi_{ab}(T \leq T_N)$ thus obtained from MFT is plotted versus T for $T \leq T_N$ as the solid curve in Fig. 5. The fit is seen to be in good agreement with the data.

We now estimate the intralayer and interlayer Heisenberg exchange interactions within a minimal J_0 - J_{z1} - J_{z2} MFT model for a helix [1, 2], where J_0 is the sum of all Heisenberg exchange interactions of a representative spin to all other spins in the same spin layer perpendicular to the helix (c) axis, J_{z1} is the sum of all interactions of the spin with spins in an adjacent layer along the helix axis, and J_{z2} is the sum of all interactions of the spin with spins in a second-nearest layer [1, 2]. Within this model kd , T_N and θ_p are related to these exchange interactions by [1, 2]

$$\cos(kd) = -\frac{J_{z1}}{4J_{z2}}, \quad (3a)$$

$$T_N = -\frac{S(S+1)}{3k_B} [J_0 + 2J_{z1} \cos(kd) + 2J_{z2} \cos(2kd)], \quad (3b)$$

$$\theta_p = -\frac{S(S+1)}{3k_B} (J_0 + 2J_{z1} + 2J_{z2}), \quad (3c)$$

where a positive (negative) J corresponds to an AFM (FM) interaction. Using $S = 7/2$, $T_N = 66.5$ K, $\theta_p = 23.0$ K, the average $kd = 0.857\pi$ rad of the two kd values in Fig. 5 and solving Eqs. (3) for the three exchange constants, one obtains

$$J_0/k_B = -9.7 \text{ K}, \quad J_{z1}/k_B = 2.1 \text{ K}, \quad (4) \\ J_{z2}/k_B = 0.6 \text{ K},$$

where the above variation in kd with T for $0 < T < T_N$ is found to have a minimal effect on the derived J 's. As anticipated above, from the FM-like θ_p the net exchange constant $J_0 + 2J_{z1} + 2J_{z2} = -4.4$ K is FM, and the out-of-plane exchange constants J_{z1} and J_{z2} are both AFM.

In summary, we demonstrated from measurements on single crystals that EuCo_2P_2 is a textbook example of a noncollinear MFT helical AFM where its χ at $T \leq T_N$ is well fitted by the predictions of MFT. The $C_{\text{mag}}(T)$ data also agree well with the MFT prediction apart from weak dynamic short-range AFM ordering above T_N that is not taken into account by MFT. From the values of S , kd , T_N and θ_p we extracted values of the Heisenberg exchange constants within the J_0 - J_{z1} - J_{z2} MFT model. It would be interesting to compare these exchange constant values with the predictions of electronic structure calculations for this model system.

This research was supported by the U.S. Department of Energy, Office of Basic Energy Sciences, Division of Materials Sciences and Engineering. Ames Laboratory is operated for the U.S. Department of Energy by Iowa State University under Contract No. DE-AC02-07CH11358.

* Present address: Department of Physics and Astronomy, Louisiana State University, Baton Rouge, Louisiana 70803, USA

† Electronic address: johnston@ameslab.gov

- [1] D. C. Johnston, “Magnetic Susceptibility of Collinear and Noncollinear Heisenberg Antiferromagnets”, *Phys. Rev. Lett.* **109**, 077201 (2012).
- [2] D. C. Johnston, “Unified Molecular Field Theory for Collinear and Noncollinear Heisenberg Antiferromagnets”, *Phys. Rev. B* **91**, 064427 (2015).
- [3] Some additional fits of the MFT to experimental data beyond those given in Ref. 1 are given in the uncensored version of Ref. 2 in D. C. Johnston, “Unified Molecular Field Theory for Collinear and Noncollinear Heisenberg Antiferromagnets”, [arXiv:1407.6353v1](https://arxiv.org/abs/1407.6353).
- [4] R. J. Goetsch, V. K. Anand, and D. C. Johnston, “Antiferromagnetism in EuNiGe_3 ”, *Phys. Rev. B* **87**, 064406 (2013).
- [5] S. L. Samal, A. Pandey, D. C. Johnston, J. D. Corbett, and G. J. Miller, “Taking Advantage of Gold’s Electronegativity in $R_4\text{Mn}_{3-x}\text{Au}_{10+x}$ ($R = \text{Y, Gd, Y; } 0.2 \leq x \leq 1$)”, *Chem. Mater.* **26**, 3209 (2014).
- [6] V. K. Anand, R. S. Dhaka, Y. Lee, B. N. Harmon, A. Kaminski, and D. C. Johnston, “Physical Properties of Metallic Antiferromagnetic $\text{CaCo}_{1.86}\text{As}_2$ Single Crystals”, *Phys. Rev. B* **89**, 214409 (2014).
- [7] R. Nath, K. M. Ranjith, B. Roy, D. C. Johnston, Y. Furukawa, and A. A. Tsirlin, “Magnetic Transitions in the Spin-5/2 Frustrated Magnet BiMn_2PO_6 and Strong Lattice Softening of BiMn_2PO_6 and BiZn_2PO_6 Below 200 K”, *Phys. Rev. B* **90**, 024431 (2014).
- [8] R. J. Goetsch, V. K. Anand, and D. C. Johnston, “Helical Antiferromagnetic Ordering in $\text{Lu}_{1-x}\text{Sc}_x\text{MnSi}$ ($x = 0, 0.25, 0.5$)”, *Phys. Rev. B* **90**, 064415 (2014).
- [9] V. K. Anand and D. C. Johnston, “Antiferromagnetism in EuCu_2As_2 and $\text{EuCu}_{1.82}\text{Sb}_2$ Single Crystals”, *Phys. Rev. B* **91**, 184403 (2015).
- [10] O. Bednarchuk and D. Kaczorowski, “Strongly Anisotropic and Complex Magnetic Behavior in EuRhGe_3 ”, *J. Alloys Compd.* **646**, 291 (2015).
- [11] M. Reehuis, W. Jeitschko, M. H. Möller, and P. J. Brown, “A Neutron Diffraction Study of the Magnetic Structure of EuCo_2P_2 ”, *J. Phys. Chem. Solids* **53**, 687 (1992).
- [12] R. Marchand and W. Jeitschko, “Ternary Lanthanoid-Transition Metal Pnictides with ThCr_2Si_2 -Type Structure”, *J. Solid State Chem.* **24**, 351 (1978).
- [13] D. C. Johnston, “Magnetic Dipole Interactions in Crystals”, [arXiv:1505.00498](https://arxiv.org/abs/1505.00498).
- [14] E. Mörsen, B. D. Mosel, W. Müller-Warmuth, M. Reehuis, and W. Jeitschko, “Mössbauer and Magnetic Susceptibility Investigations of Strontium, Lanthanum and Europium Transition Metal Phosphides with ThCr_2Si_2 Type Structure”, *J. Phys. Chem. Solids* **49**, 785 (1988).
- [15] T. Nakama, T. Yoshida, A. Ohno, D. Nakamura, Y. Takaesu, M. Hedou, K. Yagasaki, K. Uchima, T. Fujiwara, and T. Shigeoka, “Effect of Pressure on Thermopower and Resistivity of EuCo_2P_2 ”, *J. Phys.: Conf. Ser.* **200**, 032050 (2010).